

In-situ carbon coating of flame made LiMn_2O_4 nano-particles for batteries

O. Waser, R. Büchel, F. Krumeich and S.E. Pratsinis

Particle Technology Laboratory, Department of Mechanical and Process Engineering, ETH Zurich, Sonneggstrasse 3, CH-8092, Zurich, Switzerland

Keywords: flame spray pyrolysis, nanocomposites, coatings, carbon black.

Mobile, safe and non-toxic energy storage with higher specific energy and power is demanded for evolving devices. Rechargeable Li-ion batteries with nanosized LiMn_2O_4 as active cathode material can fulfil these requirements (Shen *et al.*, 2001). The capacity fading, however, by material decomposition (Amine *et al.*, 2004) currently limits its life cycle. Its carbon coating can prevent the Mn-ion dissolution into the electrolyte (Han *et al.*, 2007).

Here, a fast and single-step synthesis method to continuously produce carbon coated nano- LiMn_2O_4 is presented (Ernst *et al.* 2008). Figure 1 shows the setup that can be divided into an oxygen rich particle formation zone in the bottom and an oxygen lean coating zone at the top, after acetylene injection. In the oxygen rich zone a flame spray pyrolysis (FSP) unit produces core LiMn_2O_4 particles (Ernst *et al.* 2007) which are in-situ coated upstream in the tube with carbon black by partially oxidizing acetylene. Enclosing the FSP reactor is needed to precisely control the oxygen content otherwise no carbon black can be formed because of air entrainment from the turbulent FSP flame (Ernst *et al.* 2008). To avoid post combustion of carbon the hot off-gas is cooled with nitrogen quench gas. The coated particles were collected on a glass-fibre (GF) filter with the aid of a vacuum pump.

The resulting powders were analyzed by XRD, BET, TGA and TEM. Multiple phases of Li-Mn-O were detected by XRD (LiMn_2O_4 , LiMnO_2 , Mn_3O_4 and MnO) as a result of LiMn_2O_4 reduction in the presence of acetylene at elevated temperatures whereby the degree of reduction could be controlled by the length of the coating zone. Particles with d_{BET} of approximately 50 nm and a coating-layer thickness of 5 to 15 nm (evaluated from TEM images) were produced.

We kindly acknowledge financial support by ETH Zürich (TH-09 06-2) and thank the Electron Microscopy Center of ETH Zurich (EMEZ) for the infrastructure.

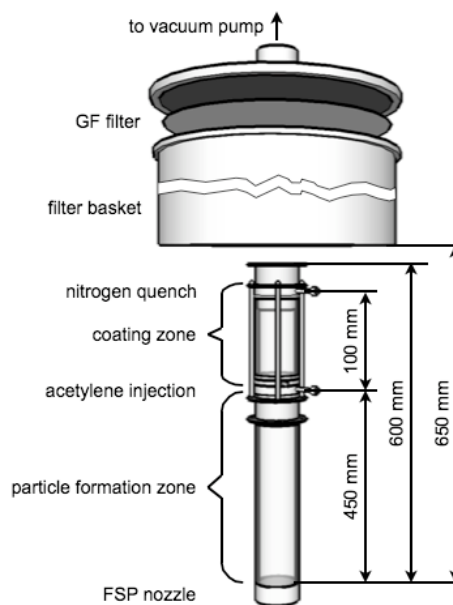


Figure 1. FSP setup for single-step synthesis of CB coated Li-Mn-O nano particles.

- Amine, K., Liu, J., Kang, S., Belharouak, I., Hyung, Y., Vissers, D., & Henriksen, G. (2004). *Improved Lithium Manganese Oxide Spinel/Graphite Li-ion Cells for High Power Applications*. *Journal of Power Sources*, 192(1), 14-19.
- Ernst, F. O., Kammler, H. K., Roessler, A., Pratsinis, S. E., Stark, W. J., Ufheil, J., Novak, P. (2007). *Electrochemically active flame-made nanosized spinels: LiMn_2O_4 , $\text{Li}_4\text{Ti}_5\text{O}_{12}$ and LiFe_5O_8* . *Materials Chemistry and Physics* 101(2-3), 372-378.
- Ernst, F. O., Buechel, R., Strobel, R., Pratsinis, S. E., (2008). *One-step flame-synthesis of carbon-embedded and -supported platinum clusters*. *Chemistry of Materials* 20(6), 2117-2123.
- Han, A. R., Kim, T. W., Park, D. H., Hwang, S. J. & Choy, J. H. (2007). *Soft Chemical Dehydration Route to Carbon Coating of Metal Oxides: Its Application for Spinel Lithium Manganate*. *Journal of Physical Chemistry C*, 111(30), 11347-11352.
- Shen, C. H., Liu, R. S., Gundakaram, R., Chen, J. M., Huang, S. M., Chen, J. S., & Wang C. M. (2001). *Effect of Co doping in LiMn_2O_4* . *Journal of Power Sources*, 102(1-2), 21-28.